

1512 S BATAVIA AVENUE  
GENEVA, IL 60134  
630-232-0104

## Test Report

[www.riverbankacoustics.com](http://www.riverbankacoustics.com)

FOUNDED 1918 BY  
WALLACE CLEMENT SABINE

SPONSOR: **ARTIZIN™**  
Garland, TX

**Sound Absorption**  
**RAL™-A22-485**

CONDUCTED: 2022-11-04

Page 1 of 9

ON: ArtFelt™ Duo 18mm Acoustic Panel

### TEST METHODOLOGY

Riverbank Acoustical Laboratories™ is accredited by the U.S. Department of Commerce, National Institute of Standards and Technology (NIST) under the National Voluntary Laboratory Accreditation Program (NVLAP) as an ISO 17025:2017 Laboratory (NVLAP Lab Code: 100227-0) and for this test procedure. The test reported in this document conformed explicitly with ASTM C423-22: "Standard Test Method for Sound Absorption and Sound Absorption Coefficients by the Reverberation Room Method." The specimen mounting was performed according to ASTM E795-16: "Standard Practices for Mounting Test Specimens During Sound Absorption Tests." A description of the measurement procedure and room specifications are available upon request. The results presented in this report apply to the sample as received from the test sponsor.

### INFORMATION PROVIDED BY SPONSOR

The test specimen was designated by the sponsor as ArtFelt™ Duo 18mm Acoustic Panel. The following nominal product information was provided by the sponsor prior to testing. The accuracy of such sponsor-provided information can affect the validity of the test results.

#### **Product Under Test**

---

Product Name: ArtFelt™ Duo 18mm Acoustic Panel  
Core Material: PET  
Thickness: 18mm  
Dimensions: 48"x96"  
Manufacturer: ARTIZIN™

### SPECIMEN MEASUREMENTS & TEST CONDITIONS

Through a full external visual inspection performed on the test specimen, Riverbank personnel verified the following information:

#### **Solid Panels**

---

Dimensions: 2 panels @ 1219 mm (48 in.) by 2438 mm (96 in.)  
Thickness: 9.4 mm (0.37 in.)  
Overall Weight: 11.79 kg (26 lbs)  
Mass per Unit Volume: 211 kg/m<sup>3</sup> (13.2 lbs/ft<sup>3</sup>)



RIVERBANK ACOUSTICAL LABORATORIES IS ACCREDITED BY NVLAP (LAB CODE 100227-0) FOR ACOUSTICAL TESTING SERVICES IN ACCORDANCE WITH ISO/IEC 17025:2017 AND FOR THIS PROCEDURE. THIS REPORT MUST NOT BE USED BY THE CLIENT TO CLAIM PRODUCT CERTIFICATION, APPROVAL, OR ENDORSEMENT BY RAL, NVLAP, NIST, OR ANY AGENCY OF THE U.S. GOVERNMENT. THIS REPORT SHALL NOT BE MODIFIED WITHOUT THE WRITTEN APPROVAL OF RAL. THE RESULTS REPORTED APPLY ONLY TO THE SPECIFIC SAMPLE SUBMITTED FOR TESTING; RAL ASSUMES NO RESPONSIBILITY FOR THE PERFORMANCE OF ANY OTHER SAMPLE.

1512 S BATAVIA AVENUE  
GENEVA, IL 60134  
630-232-0104

## Test Report

[www.riverbankacoustics.com](http://www.riverbankacoustics.com)

FOUNDED 1918 BY  
WALLACE CLEMENT SABINE

ARTIZIN™  
2022-11-04

RAL™-A22-485  
Page 2 of 9

### Patterned Panels

Dimensions: 2 panels @ 1219 mm (48 in.) by 2438 mm (96 in.)  
Thickness: 9.26 mm (0.3645 in.)  
Overall Weight: 10.43 kg (23 lbs)  
Mass per Unit Volume: 190 kg/m<sup>3</sup> (11.8 lbs/ft<sup>3</sup>)  
Installation: Laid over solid panels

### Overall Specimen Properties

Size: 2.44 m (96.0 in) wide by 2.44 m (96.0 in) long  
Thickness: 0.02 m (0.7345 in)  
Weight: 22.23 kg (49.0 lbs)  
Mass per Unit Area: 3.74 kg/m<sup>2</sup> (0.77 lbs/ft<sup>2</sup>)  
Calculation Area: 5.946 m<sup>2</sup> (64. ft<sup>2</sup>)

### Test Environment

Room Volume: 291.98 m<sup>3</sup>  
Temperature: 21.4 °C ± 0.1 °C (Requirement: ≥ 10 °C and ≤ 5 °C change)  
Relative Humidity: 56.95 % ± 0.1 % (Requirement: ≥ 40 % and ≤ 5 % change)  
Barometric Pressure: 98.3 kPa (Requirement not defined)

### MOUNTING METHOD

Type A Mounting: The test specimen was laid directly against the test surface. Perimeter edges were sealed with metal framing and tape.

1512 S BATAVIA AVENUE  
GENEVA, IL 60134  
630-232-0104

## Test Report

[www.riverbankacoustics.com](http://www.riverbankacoustics.com)

FOUNDED 1918 BY  
WALLACE CLEMENT SABINE

ARTIZIN™  
2022-11-04

RAL™-A22-485  
Page 3 of 9



Figure 1 – Specimen mounted in test chamber

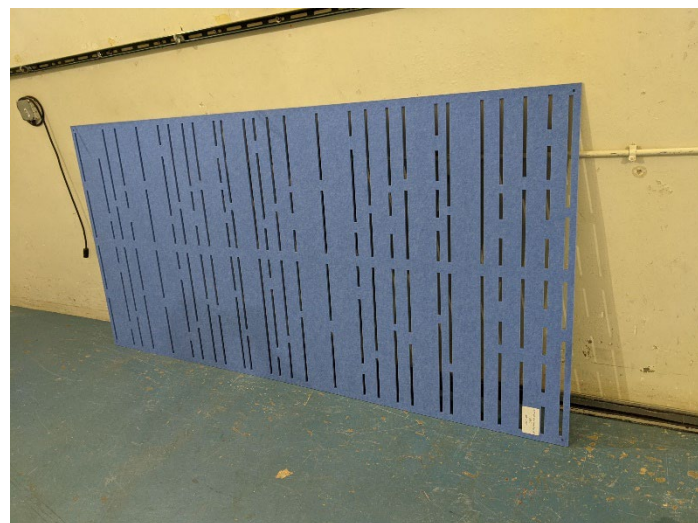


Figure 2 – Individual specimen panels, solid (left) and patterned (right)

1512 S BATAVIA AVENUE  
GENEVA, IL 60134  
630-232-0104

## Test Report

[www.riverbankacoustics.com](http://www.riverbankacoustics.com)

FOUNDED 1918 BY  
WALLACE CLEMENT SABINE

ARTIZIN™  
2022-11-04

RAL™-A22-485  
Page 4 of 9

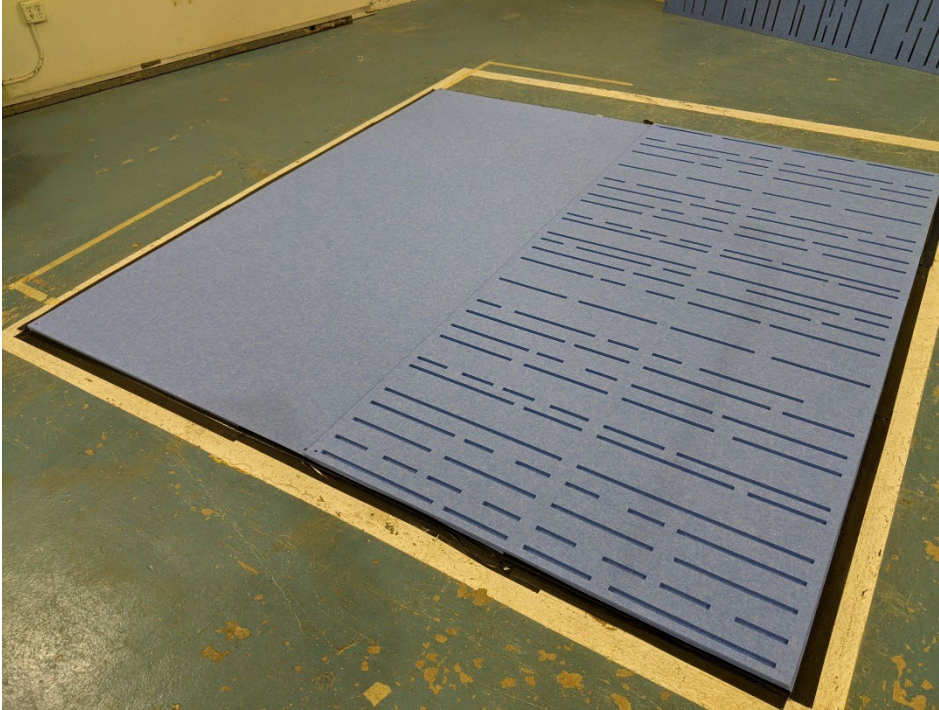


Figure 3 – Specimen patterned panels partially installed over solid panels



Figure 4 – Detail of specimen materials

1512 S BATAVIA AVENUE  
 GENEVA, IL 60134  
 630-232-0104

## Test Report

[www.riverbankacoustics.com](http://www.riverbankacoustics.com)

FOUNDED 1918 BY  
 WALLACE CLEMENT SABINE

ARTIZIN™  
 2022-11-04

RAL™-A22-485  
 Page 5 of 9

### TEST RESULTS

Specimen total absorption and absorption coefficient are tabulated at the eighteen standard frequencies. A graphic presentation of the data and additional information appear on the following pages.

1/3 Octave Center Frequency (Hz)	Total Absorption (m <sup>2</sup> )	Total Absorption (Sabins)	Absorption Coefficient
100	-0.30	-3.25	-0.05
** 125	0.11	1.13	0.02
160	0.13	1.40	0.02
200	0.31	3.33	0.05
** 250	0.60	6.41	0.10
315	1.23	13.26	0.21
400	1.57	16.90	0.26
** 500	2.49	26.80	0.42
630	3.50	37.71	0.59
800	4.37	47.05	0.74
** 1000	4.94	53.19	0.83
1250	5.75	61.87	0.97
1600	6.05	65.13	1.02
** 2000	6.28	67.63	1.06
2500	6.26	67.41	1.05
3150	6.43	69.20	1.08
** 4000	6.32	68.00	1.06
5000	6.25	67.32	1.05

**SAA = 0.61**  
**NRC = 0.60**

1512 S BATAVIA AVENUE  
GENEVA, IL 60134  
630-232-0104

## Test Report

[www.riverbankacoustics.com](http://www.riverbankacoustics.com)

FOUNDED 1918 BY  
WALLACE CLEMENT SABINE

**ARTIZIN™**  
2022-11-04

**RAL™-A22-485**  
Page 6 of 9


### TEST RESULTS (continued)


The sound absorption average (SAA) is defined in ASTM C423-17 Section 3.1.1 as the arithmetic average of the sound absorption coefficients of a material for the twelve one-third octave bands from 200 Hz through 2500 Hz, inclusive, rounded to the nearest integer multiple of 0.01.

The noise reduction coefficient (NRC) is defined from previous versions of ASTM C423 as the arithmetic average of the sound absorption coefficients at 250 Hz, 500 Hz, 1000 Hz, and 2000 Hz, rounded to the nearest integer multiple of 0.05.

Tested by   
Marc Sciaky  
Senior Experimentalist

Report by   
Keith Kimberling  
Test Engineer

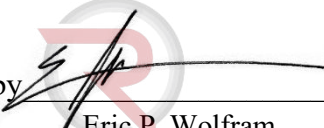Approved by   
Eric P. Wolfram  
Laboratory Manager

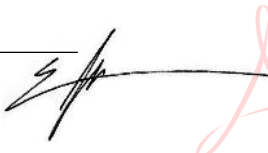  
Digitally signed by  
Eric P Wolfram  
Date: 2022.11.29  
13:59:23 -06'00'

1512 S BATAVIA AVENUE  
GENEVA, IL 60134  
630-232-0104

## Test Report


[www.riverbankacoustics.com](http://www.riverbankacoustics.com)

FOUNDED 1918 BY  
WALLACE CLEMENT SABINE

ARTIZIN™  
2022-11-04

RAL™-A22-485  
Page 7 of 9

### SOUND ABSORPTION REPORT ArtFelt™ Duo 18mm Acoustic Panel

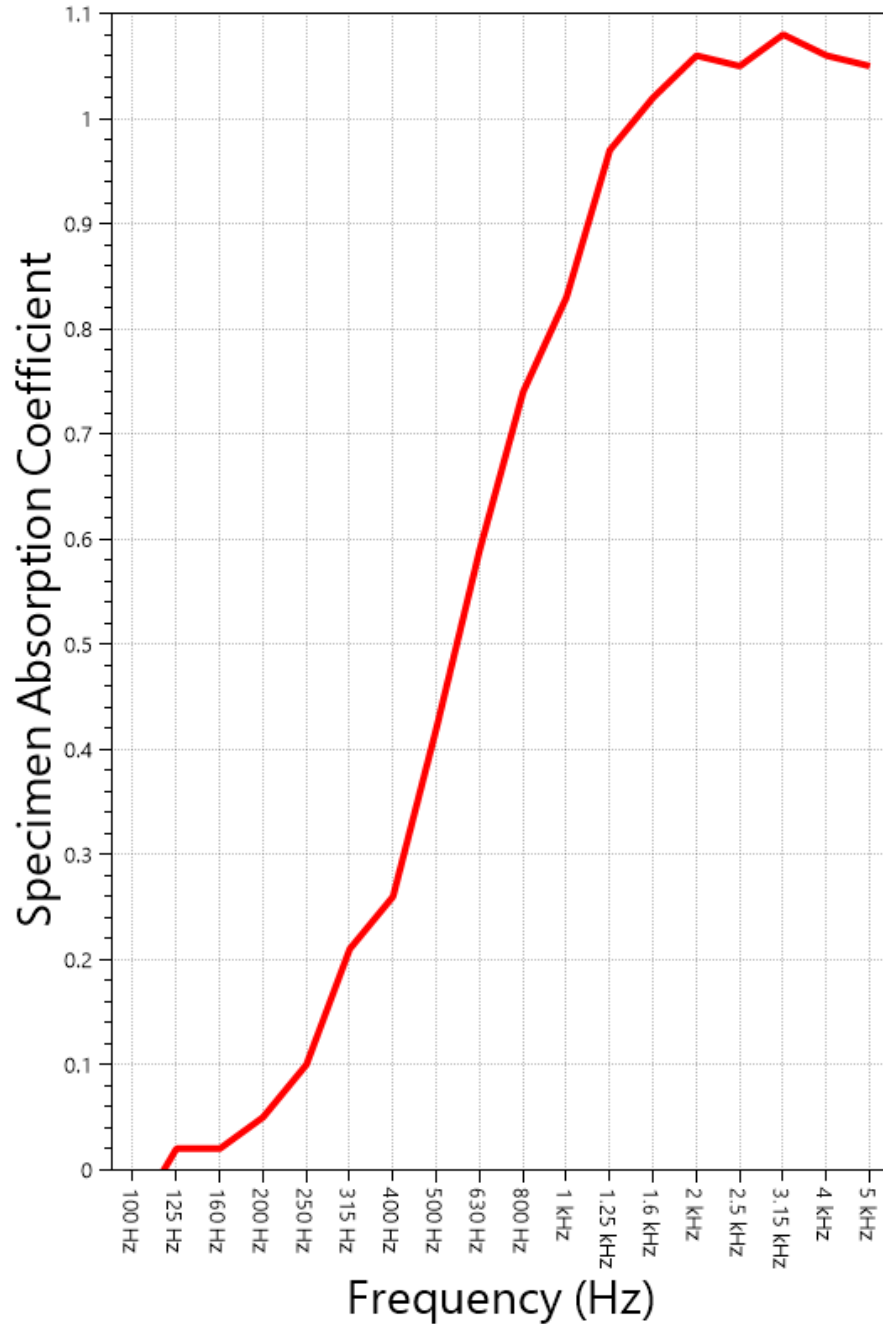

**SAA = 0.61**  
**NRC = 0.60**



RIVERBANK ACOUSTICAL LABORATORIES IS ACCREDITED BY NVLAP (LAB CODE 100227-0) FOR ACOUSTICAL TESTING SERVICES IN ACCORDANCE WITH ISO/IEC 17025:2017 AND FOR THIS PROCEDURE. THIS REPORT MUST NOT BE USED BY THE CLIENT TO CLAIM PRODUCT CERTIFICATION, APPROVAL, OR ENDORSEMENT BY RAL, NVLAP, NIST, OR ANY AGENCY OF THE U.S. GOVERNMENT. THIS REPORT SHALL NOT BE MODIFIED WITHOUT THE WRITTEN APPROVAL OF RAL. THE RESULTS REPORTED APPLY ONLY TO THE SPECIFIC SAMPLE SUBMITTED FOR TESTING; RAL ASSUMES NO RESPONSIBILITY FOR THE PERFORMANCE OF ANY OTHER SAMPLE.

1512 S BATAVIA AVENUE  
 GENEVA, IL 60134  
 630-232-0104

## Test Report

[www.riverbankacoustics.com](http://www.riverbankacoustics.com)

FOUNDED 1918 BY  
 WALLACE CLEMENT SABINE

ARTIZIN™  
 2022-11-04

RAL™-A22-485  
 Page 8 of 9

### APPENDIX A: Extended Frequency Range Data

Specimen: ArtFelt™ Duo 18mm Acoustic Panel (See Full Report)

*The following non-accredited data were obtained in accordance with ASTM C423-22, but extend beyond the defined frequency range of 100Hz to 5,000Hz. These unofficial results are representative of the RAL test environment only and intended for research & comparison purposes.*

1/3 Octave Band Center Frequency (Hz)	Total Absorption (Sabins)	Absorption Coefficient
31.5	3.59	0.06
40	2.69	0.04
50	1.22	0.02
63	-3.92	-0.06
80	0.96	0.02
100	-3.25	-0.05
125	1.13	0.02
160	1.40	0.02
200	3.33	0.05
250	6.41	0.10
315	13.26	0.21
400	16.90	0.26
500	26.80	0.42
630	37.71	0.59
800	47.05	0.74
1000	53.19	0.83
1250	61.87	0.97
1600	65.13	1.02
2000	67.63	1.06
2500	67.41	1.05
3150	69.20	1.08
4000	68.00	1.06
5000	67.32	1.05
6300	68.25	1.07
8000	68.23	1.07
10000	67.05	1.05
12500	68.34	1.07



1512 S BATAVIA AVENUE  
GENEVA, IL 60134  
630-232-0104

## Test Report

[www.riverbankacoustics.com](http://www.riverbankacoustics.com)

FOUNDED 1918 BY  
WALLACE CLEMENT SABINE

ARTIZIN™  
2022-11-04

RAL™-A22-485  
Page 9 of 9

### APPENDIX B: Instruments of Traceability

Specimen: ArtFelt™ Duo 18mm Acoustic Panel (See Full Report)

<u>Description</u>	<u>Model</u>	<u>Serial Number</u>	<u>Date of Certification</u>	<u>Calibration Due</u>
System 1	Type 3160-A-042	3160-106968	2022-07-12	2023-07-12
Bruel & Kjaer Mic And Preamp C	Type 4943-B-001	2311439	2022-05-02	2023-05-02
Bruel & Kjaer Pistonphone	Type 4228	2781248	2022-07-22	2023-07-22
EXTECH Hygro 959	SD700	A099959	2022-03-22	2023-03-22

### APPENDIX C: Revisions to Original Test Report

Specimen: ArtFelt™ Duo 18mm Acoustic Panel (See Full Report)

<u>Date</u>	<u>Revision</u>
2022-11-09	Original report issued

---

END