1512 S BATAVIA AVENUE GENEVA, IL 60134 630-232-0104

SPONSOR: ARTIZINTM

Garland, TX CONDUCTED: 2022-11-04

ON: ArtFeltTM 9mm Acoustic Panel

TEST METHODOLOGY

Riverbank Acoustical Laboratories[™] is accredited by the U.S. Department of Commerce, National Institute of Standards and Technology (NIST) under the National Voluntary Laboratory Accreditation Program (NVLAP) as an ISO 17025:2017 Laboratory (NVLAP Lab Code: 100227-0) and for this test procedure. The test reported in this document conformed explicitly with ASTM C423-22: "Standard Test Method for Sound Absorption and Sound Absorption Coefficients by the Reverberation Room Method." The specimen mounting was performed according to ASTM E795-16: "Standard Practices for Mounting Test Specimens During Sound Absorption Tests." A description of the measurement procedure and room specifications are available upon request. The results presented in this report apply to the sample as received from the test sponsor.

INFORMATION PROVIDED BY SPONSOR

The test specimen was designated by the sponsor as ArtFeltTM 9mm Acoustic Panel. The following nominal product information was provided by the sponsor prior to testing. The accuracy of such sponsor-provided information can affect the validity of the test results.

Product Under Test

Product Name:ArtFelt™ 9mm Acoustic PanelCore Material:PETThickness:9mmDimensions:48"x96"Manufacturer:ARTIZIN™

SPECIMEN MEASUREMENTS & TEST CONDITIONS

Through a full external visual inspection performed on the test specimen, Riverbank personnel verified the following information:

Test Specimen

 Dimensions:
 2 panels @ 1219 mm (48 in.) by 2438 mm (96 in.)

 Thickness:
 9.4 mm (0.37 in.)

 Overall Weight:
 11.79 kg (26 lbs)

 Mass per Unit Volume:
 211 kg/m³ (13.2 lbs/ft³)



RIVERBANK ACOUSTICAL LABORATORIES IS ACCREDITED BY NVLAP (LAB CODE 100227-0) FOR ACOUSTICAL TESTING SERVICES IN ACCORDANCE WITH ISO/IEC 17025:2017 AND FOR THIS PROCEDURE. THIS REPORT MUST NOT BE USED BY THE CLIENT TO CLAIM PRODUCT CERTIFICATION, APPROVAL, OR ENDORSEMENT BY RAL, NVLAP, NIST, OR ANY AGENCY OF THE U.S. GOVERNMENT. THIS REPORT SHALL NOT BE MODIFIED WITHOUT THE WRITTEN APPROVAL OF RAL. THE RESULTS REPORTED APPLY ONLY TO THE SPECIFIC SAMPLE SUBMITTED FOR TESTING; RAL ASSUMES NO RESPONSIBILITY FOR THE PERFORMANCE OF ANY OTHER SAMPLE.

www.riverbankacoustics.com

FOUNDED 1918 BY WALLACE CLEMENT SABINE

Sound Absorption <u>RALTM-A22-484</u>

Page 1 of 9

Test Report

1512 S BATAVIA AVENUE GENEVA, IL 60134

630-232-0104

ARTIZINTM

2022-11-04

Test Report

www.riverbankacoustics.com

FOUNDED 1918 BY WALLACE CLEMENT SABINE

RALTM-A22-484

Page 2 of 9

Overall Specimen Properties

Size: 2.44 m (96.0 in) wide by 2.44 m (96.0 in) long Thickness: 0.01 m (0.37 in) Weight: 11.79 kg (26.0 lbs) Mass per Unit Area: 1.98 kg/m² (0.41 lbs/ft²) Calculation Area: 5.946 m² (64. ft²)

Test Environment

Room Volume:	291.98 m ³
Temperature:	21.3 °C \pm 0.1 °C (Requirement: \geq 10 °C and \leq 5 °C change)
Relative Humidity:	$58.35 \% \pm 1.9 \%$ (Requirement: $\ge 40 \%$ and $\le 5 \%$ change)
Barometric Pressure:	98.4 kPa (Requirement not defined)

MOUNTING METHOD

Type A Mounting: The test specimen was laid directly against the test surface. Perimeter edges were sealed with metal framing and tape.



INVERBANK ACOUSTICAL LABORATORIES IS ACCREDITED BY NVLAP (LAB CODE 100227-0) FOR ACOUSTICAL TESTING SERVICES IN ACCORDANCE WITH ISO/IEC 17025:2017 AND FOR THIS PROCEDURE. THIS REPORT MUST NOT BE USED BY THE CLIENT TO CLAIM PRODUCT CERTIFICATION, APPROVAL, OR ENDORSEMENT BY RAL, NVLAP, NIST, OR ANY AGENCY OF THE U.S. GOVERNMENT. THIS REPORT SHALL NOT BE MODIFIED WITHOUT THE WRITTEN APPROVAL OF RAL. THE RESULTS REPORTED APPLY ONLY TO THE SPECIFIC SAMPLE SUBMITTED FOR TESTING; RAL ASSUMES NO RESPONSIBILITY FOR THE PERFORMANCE OF ANY OTHER SAMPLE.

1512 S BATAVIA AVENUE GENEVA, IL 60134

630-232-0104

Test Report

www.riverbankacoustics.com

FOUNDED 1918 BY WALLACE CLEMENT SABINE

RALTM-A22-484

Page 3 of 9

ARTIZIN^{тм} 2022-11-04

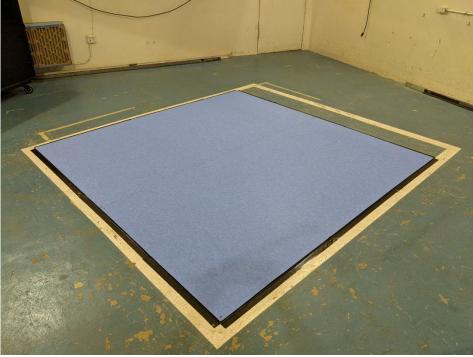


Figure 1 - Specimen mounted in test chamber



Figure 2 – Individual specimen panel



(B) RIVERBANK ACOUSTICAL LABORATORIES IS ACCREDITED BY NVLAP (LAB CODE 100227-0) FOR ACOUSTICAL TESTING SERVICES IN ACCORDANCE WITH ISO/IEC 17025:2017 AND FOR THIS PROCEDURE. THIS REPORT MUST NOT BE USED BY THE CLIENT TO CLAIM PRODUCT CERTIFICATION, APPROVAL, OR ENDORSEMENT BY RAL, NVLAP, NIST, OR ANY AGENCY OF THE U.S. GOVERNMENT. THIS REPORT SHALL NOT BE MODIFIED WITHOUT THE WRITTEN APPROVAL OF RAL. THE RESULTS REPORTED APPLY ONLY TO THE SPECIFIC SAMPLE SUBMITTED FOR TESTING; RAL ASSUMES NO RESPONSIBILITY FOR THE PERFORMANCE OF ANY OTHER SAMPLE.

1512 S BATAVIA AVENUE GENEVA, IL 60134

ARTIZINTM

2022-11-04

630-232-0104

Test Report

www.riverbankacoustics.com

FOUNDED 1918 BY WALLACE CLEMENT SABINE

RALTM-A22-484

Page 4 of 9



Figure 3 – Detail of specimen material



INVERBANK ACOUSTICAL LABORATORIES IS ACCREDITED BY NVLAP (LAB CODE 100227-0) FOR ACOUSTICAL TESTING SERVICES IN ACCORDANCE WITH ISO/IEC 17025:2017 AND FOR THIS PROCEDURE. THIS REPORT MUST NOT BE USED BY THE CLIENT TO CLAIM PRODUCT CERTIFICATION, APPROVAL, OR ENDORSEMENT BY RAL, NVLAP, NIST, OR ANY AGENCY OF THE U.S. GOVERNMENT. THIS REPORT SHALL NOT BE MODIFIED WITHOUT THE WRITTEN APPROVAL OF RAL. THE RESULTS REPORTED APPLY ONLY TO THE SPECIFIC SAMPLE SUBMITTED FOR TESTING; RAL ASSUMES NO RESPONSIBILITY FOR THE PERFORMANCE OF ANY OTHER SAMPLE.

Test Report

1512 S BATAVIA AVENUE GENEVA, IL 60134

630-232-0104

ARTIZINTM

2022-11-04

TEST RESULTS

Specimen total absorption and absorption coefficient are tabulated at the eighteen standard frequencies. A graphic presentation of the data and additional information appear on the following pages.

1/3 Octave Center			
Frequency	Total Absorption	Total Absorption	Absorption
(Hz)	$(m^2)^{-1}$	(Sabins)	Coefficient
100	0.52	5 50	0.00
100	-0.52	-5.59	-0.09
** 125	0.36	3.84	0.06
160	-0.02	-0.24	0.00
200	0.03	0.32	0.00
** 250	0.20	2.15	0.03
315	0.42	4.47	0.07
400	0.44	4.72	0.07
** 500	0.83	8.94	0.14
630	1.09	11.75	0.14
030	1.09	11.75	0.18
800	1.61	17.28	0.27
** 1000	2.30	24.81	0.39
1250	3.14	33.84	0.53
1600	3.78	40.72	0.64
** 2000	4.24	45.66	0.71
2500	4.76	51.22	0.80
2500	4.70	51.22	0.80
3150	5.39	57.97	0.91
** 4000	5.63	60.64	0.95
5000	6.22	66.99	1.05
	SAA	= 0.32	

SAA = 0.32NRC = 0.30



(B) RIVERBANK ACOUSTICAL LABORATORIES IS ACCREDITED BY NVLAP (LAB CODE 100227-0) FOR ACOUSTICAL TESTING SERVICES IN ACCORDANCE WITH ISO/IEC 17025:2017 AND FOR THIS PROCEDURE. THIS REPORT MUST NOT BE USED BY THE CLIENT TO CLAIM PRODUCT CERTIFICATION, APPROVAL, OR ENDORSEMENT BY RAL, NVLAP, NIST, OR ANY AGENCY OF THE U.S. GOVERNMENT. THIS REPORT SHALL NOT BE MODIFIED WITHOUT THE WRITTEN APPROVAL OF RAL. THE RESULTS REPORTED APPLY ONLY TO THE SPECIFIC SAMPLE SUBMITTED FOR TESTING; RAL ASSUMES NO RESPONSIBILITY FOR THE PERFORMANCE OF ANY OTHER SAMPLE.

www.riverbankacoustics.com

FOUNDED 1918 BY WALLACE CLEMENT SABINE

<u>RAL^{тм}-A22-484</u>

Page 5 of 9

Test Report

1512 S BATAVIA AVENUE GENEVA, IL 60134

630-232-0104

ARTIZIN™ 2022-11-04

TEST RESULTS (continued)

The sound absorption average (SAA) is defined in ASTM C423-17 Section 3.1.1 as the arithmetic average of the sound absorption coefficients of a material for the twelve one-third octave bands from 200 Hz through 2500 Hz, inclusive, rounded to the nearest integer multiple of 0.01.

The noise reduction coefficient (NRC) is defined from previous versions of ASTM C423 as the arithmetic average of the sound absorption coefficients at 250 Hz, 500 Hz, 1000 Hz, and 2000 Hz, rounded to the nearest integer multiple of 0.05.

Tested by Marc Sciaky Marc Sciaky Senior Experimentalist	Report by Keith Kimberling Test Engineer
Approved by Eric P. Wo Laboratory	



INVERBANK ACOUSTICAL LABORATORIES IS ACCREDITED BY NVLAP (LAB CODE 100227-0) FOR ACOUSTICAL TESTING SERVICES IN ACCORDANCE WITH ISO/IEC 17025:2017 AND FOR THIS PROCEDURE. THIS REPORT MUST NOT BE USED BY THE CLIENT TO CLAIM PRODUCT CERTIFICATION, APPROVAL, OR ENDORSEMENT BY RAL, NVLAP, NIST, OR ANY AGENCY OF THE U.S. GOVERNMENT. THIS REPORT SHALL NOT BE MODIFIED WITHOUT THE WRITTEN APPROVAL OF RAL. THE RESULTS REPORTED APPLY ONLY TO THE SPECIFIC SAMPLE SUBMITTED FOR TESTING; RAL ASSUMES NO RESPONSIBILITY FOR THE PERFORMANCE OF ANY OTHER SAMPLE.

www.riverbankacoustics.com

FOUNDED 1918 BY WALLACE CLEMENT SABINE

RALTM-A22-484 Page 6 of 9

1512 S BATAVIA AVENUE GENEVA, IL 60134

630-232-0104

ARTIZINTM

2022-11-04


Test Report

www.riverbankacoustics.com

FOUNDED 1918 BY WALLACE CLEMENT SABINE

RALTM-A22-484

Page 7 of 9

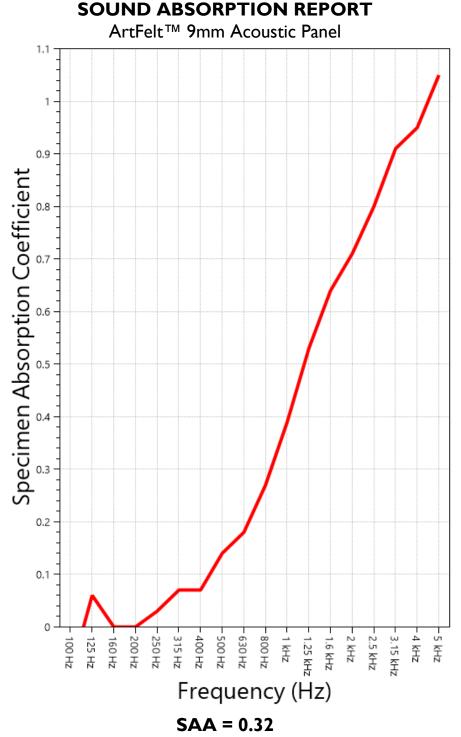

NRC = 0.30



(B) RIVERBANK ACOUSTICAL LABORATORIES IS ACCREDITED BY NVLAP (LAB CODE 100227-0) FOR ACOUSTICAL TESTING SERVICES IN ACCORDANCE WITH ISO/IEC 17025:2017 AND FOR THIS PROCEDURE. THIS REPORT MUST NOT BE USED BY THE CLIENT TO CLAIM PRODUCT CERTIFICATION, APPROVAL, OR ENDORSEMENT BY RAL, NVLAP, NIST, OR ANY AGENCY OF THE U.S. GOVERNMENT. THIS REPORT SHALL NOT BE MODIFIED WITHOUT THE WRITTEN APPROVAL OF RAL. THE RESULTS REPORTED APPLY ONLY TO THE SPECIFIC SAMPLE SUBMITTED FOR TESTING; RAL ASSUMES NO RESPONSIBILITY FOR THE PERFORMANCE OF ANY OTHER SAMPLE.

Test Report

1512 S BATAVIA AVENUE GENEVA, IL 60134

630-232-0104

ARTIZINTM

2022-11-04

APPENDIX A: Extended Frequency Range Data

Specimen: ArtFelt[™] 9mm Acoustic Panel (See Full Report)

The following non-accredited data were obtained in accordance with ASTM C423-22, but extend beyond the defined frequency range of 100Hz to 5,000Hz. These unofficial results are representative of the RAL test environment only and intended for research & comparison purposes.

1/3 Octave Band Center Frequency (Hz)	Total Absorption (Sabins)	Absorption Coefficient
31.5	2.10	0.03
40	0.38	0.01
50	-1.13	-0.02
63	-3.15	-0.05
80	-3.76	-0.06
100	-5.59	-0.09
125	3.84	0.06
160	-0.24	0.00
200	0.32	0.00
250	2.15	0.03
315	4.47	0.07
400	4.72	0.07
500	8.94	0.14
630	11.75	0.18
800	17.28	0.27
1000	24.81	0.39
1250	33.84	0.53
1600	40.72	0.64
2000	45.66	0.71
2500	51.22	0.80
3150	57.97	0.91
4000	60.64	0.95
5000	66.99	1.05
6300	69.63	1.09
8000	72.28	1.13
10000	71.81	1.12
12500	74.17	1.16



(B) RIVERBANK ACOUSTICAL LABORATORIES IS ACCREDITED BY NVLAP (LAB CODE 100227-0) FOR ACOUSTICAL TESTING SERVICES IN ACCORDANCE WITH ISO/IEC 17025:2017 AND FOR THIS PROCEDURE. THIS REPORT MUST NOT BE USED BY THE CLIENT TO CLAIM PRODUCT CERTIFICATION, APPROVAL, OR ENDORSEMENT BY RAL, NVLAP, NIST, OR ANY AGENCY OF THE U.S. GOVERNMENT. THIS REPORT SHALL NOT BE MODIFIED WITHOUT THE WRITTEN APPROVAL OF RAL. THE RESULTS REPORTED APPLY ONLY TO THE SPECIFIC SAMPLE SUBMITTED FOR TESTING; RAL ASSUMES NO RESPONSIBILITY FOR THE PERFORMANCE OF ANY OTHER SAMPLE.

www.riverbankacoustics.com

FOUNDED 1918 BY WALLACE CLEMENT SABINE

RAL[™]-A22-484

Page 8 of 9

Test Report

1512 S BATAVIA AVENUE GENEVA, IL 60134

630-232-0104

ARTIZINTM

2022-11-04

APPENDIX B: Instruments of Traceability

Specimen: ArtFelt[™] 9mm Acoustic Panel (See Full Report)

www.riverbankacoustics.com

FOUNDED 1918 BY WALLACE CLEMENT SABINE

RALTM-A22-484

Page 9 of 9

Description	Model	Serial <u>Number</u>	Date of <u>Certification</u>	Calibration <u>Due</u>
System 1	Type 3160-A-042	3160- 106968	2022-07-12	2023-07-12
Bruel & Kjaer Mic And Preamp C	Type 4943-B-001	2311439	2022-05-02	2023-05-02
Bruel & Kjaer Pistonphone EXTECH Hygro 959	Type 4228 SD700	2781248 A099959	2022-07-22 2022-03-22	2023-07-22 2023-03-22

APPENDIX C: Revisions to Original Test Report

Specimen: ArtFeltTM 9mm Acoustic Panel (See Full Report)

<u>Date</u>	Revision
<mark>2022-11-09</mark>	Original report issued

END



INVERBANK ACOUSTICAL LABORATORIES IS ACCREDITED BY NVLAP (LAB CODE 100227-0) FOR ACOUSTICAL TESTING SERVICES IN ACCORDANCE WITH ISO/IEC 17025:2017 AND FOR THIS PROCEDURE. THIS REPORT MUST NOT BE USED BY THE CLIENT TO CLAIM PRODUCT CERTIFICATION, APPROVAL, OR ENDORSEMENT BY RAL, NVLAP, NIST, OR ANY AGENCY OF THE U.S. GOVERNMENT. THIS REPORT SHALL NOT BE MODIFIED WITHOUT THE WRITTEN APPROVAL OF RAL. THE RESULTS REPORTED APPLY ONLY TO THE SPECIFIC SAMPLE SUBMITTED FOR TESTING; RAL ASSUMES NO RESPONSIBILITY FOR THE PERFORMANCE OF ANY OTHER SAMPLE.